

ISBN 978-0-626-21915-4

SANS 3575:2008

Edition 2

ISO 3575:2005

Edition 3

SOUTH AFRICAN NATIONAL STANDARD

Continuous hot-dip zinc-coated carbon steel sheet of commercial and drawing qualities

This national standard is the identical implementation of ISO 3575:2005 and is adopted with the permission of the International Organization for Standardization.

Published by SABS Standards Division
1 Dr Lategan Road Groenkloof ☒ Private Bag X191 Pretoria 0001
Tel: +27 12 428 7911 Fax: +27 12 344 1568
www.sabs.co.za
© SABS

SABS

SANS 3575:2008

Edition 2

ISO 3575:2005

Edition 3

Table of changes

Change No.	Date	Scope

National foreword

This South African standard was approved by National Committee SABS TC 107, *Metallic and other inorganic coatings*, in accordance with procedures of the SABS Standards Division, in compliance with annex 3 of the WTO/TBT agreement.

This SANS document was published in December 2008. This SANS document supersedes SABS ISO 3575:1996 (first edition).

INTERNATIONAL STANDARD

**ISO
3575**

Third edition
2005-05-15

Continuous hot-dip zinc-coated carbon steel sheet of commercial and drawing qualities

*Tôles en acier au carbone galvanisées en continu par immersion à
chaud, de qualité commerciale et pour emboutissage*



Reference number
ISO 3575:2005(E)

© ISO 2005

ISO 3575:2005(E)

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

© ISO 2005

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 3575 was prepared by Technical Committee ISO/TC 17, *Steel*, Subcommittee SC 12, *Continuous mill flat rolled products*.

This third edition cancels and replaces the second edition (ISO 3575:1996), which has been technically revised.

Continuous hot-dip zinc-coated carbon steel sheet of commercial and drawing qualities

1 Scope

1.1 This International Standard applies to carbon steel sheet of commercial and drawing qualities coated by the continuous hot-dip zinc-coating process.

1.2 Zinc-coated sheet is suitable for applications where resistance to corrosion is of prime importance.

1.3 The steel sheet is produced in a number of qualities, coating mass, surface treatments, and ordering conditions.

1.4 Zinc-coated sheet is produced in thicknesses from 0,25 mm to 5 mm inclusive after coating, and in widths of 600 mm and over in coils and cut lengths. Zinc-coated sheet less than 600 mm wide, slit from wide sheet, will be considered as sheet.

1.5 The thickness of hot-dip zinc-coated and zinc-iron alloy sheet steel may be specified as a combination of the base metal and metallic coating, or as the base metal alone. The purchaser shall indicate on the order which method of specifying thickness is required. In the event the purchaser does not indicate any preference, the thickness as a combination of the base metal and coating will be provided. Annex A describes the requirements for specifying the thickness of the base metal alone.

1.6 Zinc and zinc-iron alloy coated steel sheet may be ordered in one of two ordering conditions:

- a) Condition A): steel ordered to satisfy mechanical property requirements.
- b) Condition B): steel ordered to make an identified part.

1.7 Zinc-coated steel sheet is available in several fabrication qualities.

- Commercial: intended for general fabrication purposes where sheet is used in the flat or for bending or moderate forming.
- Drawing: intended for fabricating parts where drawing or severe forming may be involved.
- Deep drawing-aluminium killed (non-aging): intended for fabricating parts where particularly severe drawing or forming may be involved or essential freedom from aging is required.
- Extra deep drawing (stabilized interstitial free): intended for applications requiring interstitial free steel (IF) which is non-aging and has maximum formability.

1.8 This International Standard does not cover steels designated as structural quality which are covered in ISO 4998 ^[1].

ISO 3575:2005(E)

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1460:1992, *Metallic coatings — Hot dip galvanized coatings on ferrous materials — Gravimetric determination of the mass per unit area*

ISO 2178:1982, *Non-magnetic coatings on magnetic substrates — Measurement of coating thickness — Magnetic method*

ISO 3497:1990, *Metallic coatings — Measurement of coating thickness — X-ray spectrometric methods*

ISO 6892:1998, *Metallic materials — Tensile testing at ambient temperature*

ISO 7438:1985, *Metallic materials — Bend test*

ISO 16160:2000, *Continuously hot-rolled steel sheet products — Dimensional and shape tolerances*

ISO 16162:2000, *Continuously cold-rolled steel sheet products — Dimensional and shape tolerances*

ISO 16163:2000, *Continuously hot-dipped coated steel sheet products — Dimensional and shape tolerances*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1
continuous hot-dip zinc-coated steel sheet
product obtained by hot-dip zinc coating cold-reduced sheet coils or hot-rolled descaled sheet coils on a continuous zinc-coating line to produce either zinc-coated coils or zinc-coated cut lengths

3.2
breakage allowance
agreed upon level of acceptable die breakage not subject to claim

3.3
normal spangle
coating formed as a result of unrestricted growth of zinc crystals during normal solidification

NOTE This coating has a metallic lustre and is the type normally furnished for a wide variety of applications. It may be furnished S (normal coating, with skin pass) or N (normal coating, as coated); however, it may be variable in appearance and not suitable for decorative painting.

3.4
minimized spangle
coating obtained by restricting normal spangle formation during the solidification of the zinc

NOTE This product may have some lack of uniformity in surface appearance within a coil or from coil to coil.

3.5
smooth finish
smoothness produced by skin-passing the coated material in order to achieve an improved surface condition as compared with the normal as-coated product

3.6

zinc-iron alloy coating

coating produced by processing the zinc-coated steel sheet so that the coating formed on the base metal is composed of zinc-iron alloys

NOTE This product, designated ZF, is not spangled, is normally dull in appearance, and for some applications, may be suitable for immediate painting without further treatment, except normal cleaning. Zinc-iron alloy coatings may powder during severe forming.

3.7

skin pass

light cold-rolling of the zinc-coated steel sheet

NOTE The purpose of the skin pass is to produce a higher degree of surface smoothness and thereby improve the surface appearance. The skin pass also temporarily minimizes the occurrence of a surface condition known as stretcher strain (Luder's Lines) or fluting during the fabrication of finished parts. The skin pass also controls and improves flatness. Some increase in hardness and loss of ductility will result from skin passing.

3.8

differential coating

coating having a coating mass on one surface significantly different from the coating mass on the other surface

4 Requirements

4.1 Chemical composition

The chemical composition (heat analysis) shall not exceed the values given in Tables 1 and 2. On request, a report of the heat analysis shall be made to the purchaser.

A verification analysis (product analysis) may be made by the purchaser to verify the specified analysis of the semi-finished or finished steel and shall take into consideration any normal heterogeneity. Non-killed steels, such as rimmed or capped, are not technologically suited for verification analysis. The product analysis tolerances are shown in Table 3.

The processes used in making the steel and in manufacturing zinc-coated sheet are left to the discretion of the manufacturer. When requested, the purchaser shall be informed of the steelmaking process being used.

On request, a report of the heat analysis shall be made to the purchaser.

Table 1 — Chemical composition (heat analysis), %

Base-metal quality		C	Mn	P	S	Ti
Designation	Name	max.	max.	max.	max.	max.
01	Commercial	0,15	0,60	0,05	0,05	
02	Drawing	0,12	0,50	0,04	0,04	
03 ^a	Deep drawing	0,10	0,45	0,03	0,03	
04 ^a	Deep drawing special killed	0,08	0,45	0,03	0,03	
05 ^a	Extra deep drawing stabilized	0,02	0,25	0,02	0,02	0,15

^a For interstitial free steels only, the values of 0,15 % titanium, and 0,10 % maximum for niobium and vanadium are acceptable to ensure that the carbon and nitrogen are fully stabilized.

Table 2 — Limits on additional chemical elements, %

Element	Cu ^a max.	Ni ^a max.	Cr ^{a, b} max.	Mo ^{a, b} max.	Nb ^c max.	V ^{c, d} max.	Ti ^c max.
Heat analysis	0,20	0,20	0,15	0,06	0,008	0,008	0,008
Product analysis	0,23	0,23	0,19	0,07	0,018	0,018	0,018
NOTE Each of the elements listed in this table shall be included in the report of the heat analysis. When the amount of copper, nickel, chromium or molybdenum present is less than 0,02 %, the analysis may be reported as < 0,02 %.							
^a The sum of copper, nickel, chromium and molybdenum shall not exceed 0,50 % on the heat analysis. When one or more of these elements are specified, the sum does not apply, in which case, only the individual limits on the remaining elements apply.							
^b The sum of chromium and molybdenum shall not exceed 0,16 % on heat analysis. When one or more of these elements are specified, the sum does not apply, in which case, only the individual limits on the remaining elements apply.							
^c For interstitial free steels only, the value of 0,15 % titanium, and 0,10 % maximum for niobium and vanadium are acceptable to ensure that the carbon and nitrogen are fully stabilized.							
^d Heat analysis greater than 0,008 % may be supplied after agreement between the producer and purchaser.							

Table 3 — Product analysis tolerances, %

Element	Maximum of specified element	Tolerance over maximum specified
C	0,25	0,04
Mn	1,70	0,14
P	0,05	0,01
S	0,035	0,01
NOTE The above maximum tolerance is the allowable excess over the specified requirement and not the heat analysis.		

4.2 Mechanical properties

Zinc-coated sheet of designations 01, 02, 03, 04 and 05 are supplied under the following two ordering conditions:

- Ordering condition A). Steel when ordered to mechanical properties shall, at the time the steel is made available for shipment, satisfy the applicable requirements of Table 4.
- Ordering condition B). Steel when ordered to make an identified part shall be supplied with a commitment for satisfactory manufacturing performance within a proper breakage allowance, which shall be previously agreed upon by the interested parties. In these cases, the part name, the details of fabrication, and special requirements (such as freedom from stretcher strain or fluting) shall be specified.

NOTE Prolonged storage of the sheet can cause a change in mechanical properties (increase in hardness and decrease in elongation), leading to a decrease in drawability. To minimize this effect, quality 03, 04 and 05 should be specified.

Table 4 — Mechanical properties

Base-metal quality ^a		R_e max. ^b N/mm ² ^e	R_m max. ^c N/mm ²	A min ^d		
Designation	Name			$L_o = 80$ mm	$L_o = 50$ mm	$L_o = 5,65\sqrt{S_o}$ ^f
01	Commercial	—	—	—	—	—
02	Drawing	300 ^g	430	24	23	22
03	Deep drawing	260	410	26	25	24
04	Deep drawing special killed	220	410	29	28	27
05	Extra deep drawing stabilized	200	350	37	36	35
R_e = yield stress R_m = tensile strength A = percent elongation after fracture L_o = gauge length on test piece S_o = original cross-sectional area of gauge length						
NOTE 1 Time period from date of shipment for values stated in this table to be applicable. Designation Time period 01 — 02 8 days 03 1 month 04 6 months 05 6 months NOTE 2 For products produced according to performance criteria 4.2, the typical mechanical properties presented here are non-mandatory. For products specified according to mechanical properties, the purchaser may negotiate with the supplier if a specific range, or a more restrictive range, is required for the application, therefore, by agreement, these values may be specified. NOTE 3 These typical mechanical properties apply to the full range of steel sheet thicknesses. The yield tends to increase and some of the formability aspects tend to decrease as the sheet thickness decreases.						
^a All qualities are available with a minimized spangle zinc coating. ^b The yield values apply to 0,2 % proof stress if the yield point is not pronounced, otherwise to the lower yield point (R_{eL}). ^c Minimum tensile strength for qualities 02, 03, 04 and 05 would normally be expected to be 270 N/mm ² . All tensile strength values are determined to the nearest 10 N/mm ² . ^d For material up to and including 0,6 mm in thickness, the elongation values in the table shall be reduced by 2. ^e 1 N/mm ² = 1 MPa. ^f May be used for material over 3 mm in thickness. ^g This value applies to skin-passed products only.						

4.3 Coating

4.3.1 Coating mass

The coating mass limits shall conform to the limits for the designations shown in Table 5. The coating mass is the total amount of coating on both sides of the sheet, expressed in grams per square metre. The coating mass of differentially coated product shall be agreed upon by the interested parties. If a maximum coating mass is required, the manufacturer shall be notified at the time of ordering.

Table 5 — Coating mass (total both sides)

Coating designation	Minimum check limit	
	Triple-spot test g/m ² (of sheet)	Single-spot test g/m ² (of sheet)
Z001	No minimum ^a	No minimum ^a
Z100	100	85
Z180	180	150
Z200	200	170
Z275	275	235
Z350	350	300
Z450	450	385
Z600	600	510
Z700	700	595
ZF001	No minimum	No minimum
ZF100	100	85
ZF180	180	150

Because of the many variables and changing conditions that are characteristic of continuous zinc coating, the coating mass is not always evenly divided between the two surfaces of a zinc-coated sheet; neither is the zinc coating evenly distributed from edge to edge. However, it can normally be expected that not less than 40 % of the single-spot check limit will be found on either surface.

NOTE The coating thickness may be estimated from the coating mass by using the following relationship:
100 g/m² total both sides = 0,014 mm total both sides.

^a "No minimum" means that there are no established minimum check limits for triple- and single-spot tests.

4.3.2 Coating adherence

The zinc-coated sheet shall be capable of being bent in any direction, in accordance with the mandrel diameter requirements of Table 6, without flaking of the coating on the outside of the bend. Flaking of the coating within 7 mm from the edge of the test piece shall not be a cause for rejection. The bend test requirements of Table 6 do not apply to zinc-iron alloy coating.

Table 6 — Coating adherence — Bend test mandrel diameter

Base-metal quality	Coated metal –180° bend mandrel diameter mm								
	Coating designation								
	<i>e</i> < 3 mm				<i>e</i> ≥ 3 mm				
	up to Z275	Z300 Z350	Z450 Z600	Z700	up to Z275	Z300 Z350	Z450	Z600	Z700
Commercial	1 _a	1 _a	2 _a	3 _a	2 _a	2 _a	2 _a	3 _a	4 _a
Drawing	0	1 _a	2 _a	2 _a	0	1 _a	2 _a	2 _a	2 _a
Deep drawing	0	1 _a	2 _a	2 _a	0	1 _a	2 _a	2 _a	2 _a
Deep drawing special killed	0	1 _a	2 _a	2 _a	0	1 _a	2 _a	2 _a	2 _a
Extra deep drawing stabilized	0	1 _a	2 _a	2 _a	0	1 _a	2 _a	2 _a	2 _a

a = bend mandrel diameter = *e*

e = thickness of steel sheet, in millimetres

4.4 Weldability

The product is suitable for welding if appropriate welding methods and procedures are used with special attention to the heavier coatings. Zinc-iron alloyed coatings (ZF) are usually more suitable than other coatings (Z) for resistance welding.

4.5 Painting

Hot-dip zinc-coated steel sheet is a suitable base for paint, but the first treatment may be different from those used on mild steel. Pre-treatment primers, chemical conversion coatings (chromate, phosphate or oxide type), and some paints specially formulated for direct application to zinc surfaces, are all appropriate first treatments for hot-dip zinc-coated sheet. In drawing up a painting schedule, consideration shall be given to whether the hot-dip zinc-coated sheet shall be ordered passivated or not passivated.

4.6 Surface treatment

4.6.1 Mill passivation

A chemical treatment is normally applied to zinc coatings to minimize the hazard of wet-storage stain (white rust) during shipment and storage. However, the inhibiting characteristics of the treatment are limited and if a shipment is received wet, the material shall be used immediately or dried. This treatment is not usually applied to zinc-iron alloyed coatings because it interferes with the adhesion of most paints.

4.6.2 Mill phosphating

Zinc-coated steel sheet may be processed chemically at the manufacturer's works to prepare all types of coatings for painting without further treatment except normal cleaning.

4.6.3 Oiling

The zinc-coated steel sheet as produced may be oiled to prevent marring and scratching of the soft surface during handling or shipping and to minimize wet storage stain. When the zinc-coated sheet has received a passivating treatment, oiling will further minimize the hazard of wet-storage stain.

4.7 Coated coil joining

Continuous coil coating lines use various methods to join coil ends. These methods include lap welding, butt welding, and stitching. The shipment of coils containing the joined coil ends shall be permitted if agreed upon between the manufacturer and purchaser.

4.8 Dimensional and shape tolerances

4.8.1 Dimensional tolerances applicable to zinc-coated steel sheet shall be as given in ISO 16163. The tolerances for thickness apply to products whose thickness is a combination of base metal and coating thickness.

4.8.2 When the base metal thickness is specified, the thickness tolerances of Tables 6, 7 and 8 of ISO 16163:2000 shall apply to the average product thickness as calculated in accordance with Annex A. The tolerances for thickness of the base metal shall be as given in ISO 16160 for hot-rolled steel, and ISO 16162 for cold-rolled steel.

5 Sampling

5.1 Chemical composition

Each heat shall be tested by the manufacturer to determine compliance with the requirements of Tables 1 and 2.

ISO 3575:2005(E)

5.2 Tensile test

When required, one representative transverse sample from each lot for shipment shall be taken for the tensile test to verify conformance to the requirements of Table 4. Transverse test pieces shall be taken mid-way between the centre and the edge of the sheet as-rolled. A lot consists of 50 tonnes or less of sheet of the same quality rolled to the same thickness and coating condition.

5.3 Coating tests

5.3.1 Coating mass

5.3.1.1 The producer shall develop a testing plan with a frequency sufficient to adequately characterize the lot of material and ensure conformance with specification requirements.

5.3.1.2 The purchaser may conduct verification tests by securing a sample piece approximately 300 mm in length by the as-coated width and cutting three test specimens, one from the mid-width position and one from each side, not closer than 25 mm to the side edge. The minimum area of the three specimens shall be 2 000 mm².

5.3.2 Triple-spot test

The triple-spot test result shall be the average coating mass found on the three specimens taken according to 5.3.1.

5.3.3 Single-spot test

The single-spot test result shall be the minimum coating mass found on any one of the three specimens used for the triple-spot test. Material, which has been slit from wide coil, shall be subject to a single-spot test only.

5.4 Coating adherence

One representative sample for the coating-adherence bend test shall be taken from each lot of sheet for shipment. The specimens for the coated bend test shall not be taken closer than 25 mm from a side edge. The minimum width for the test specimen shall not be less than 50 mm.

5.5 Retest

If a test does not satisfy the specified results, two more test pieces shall be taken at random from the same lot. Both retests shall conform to the requirements of this International Standard.

6 Test methods

6.1 Tensile test

The tests shall be conducted in accordance with the methods specified in ISO 6892. Base-metal thickness shall be used to calculate the cross-sectional area needed for the tensile test; however, for orders specifying thickness "as base metal only", there are two permissible methods for determining the base-metal thickness:

- a) Option A — Determine the actual base-metal thickness through direct measurement of the substrate of a specimen whose coating has been removed.
- b) Option B — Calculation of the base-metal thickness through subtraction of the average coating thickness for the appropriate coating designation included in Annex A from the actual coated thickness of the test specimen.

6.2 Coating properties

6.2.1 Coating mass

The manufacturer shall conduct tests using methods deemed necessary to ensure that the material complies with the requirements shown in Table 5. Commonly used methods include ISO 1460, ISO 3497 and ISO 2178. Coating mass is determined by converting coating thickness measurements made with magnetic gauges (ISO 2178) or by X-ray spectrometry (ISO 3497) using the relationship given in Table 5.

6.2.2 Coating adherence

Bend tests shall be conducted in accordance with the methods specified in ISO 7438.

7 Designation system

The designation system includes the coating name, coating mass designation, coating finish type, surface treatment, and base-metal quality.

7.1 Coating name

The letter Z indicates a zinc coating, and the letters ZF indicate a zinc-iron alloy coating.

7.2 Coating mass

The coating mass designations for zinc coating are 001, 100, 180, 200, 275, 350, 450, 600 and 700. The coating mass designations for zinc-iron alloy coating are 001, 100 and 180.

The coating is expressed as the total mass on both surfaces, in grams per square metre. The coating mass specified should be compatible with the desired service life, the thickness of the base metal, and with the forming requirements involved.

NOTE For differential coatings, the standard would be top surface before bottom surface. An example of a differential coating designation is: Z275S100C02.

7.3 Coating finish type

The conditions of the coating designations are

- N: normal coating, as coated
- S: normal coating with skin pass
- M: minimized spangle, as produced
- E: minimized spangle with skin pass

The 'M' and 'E' coating conditions are normally furnished in designations Z350, Z275, Z200 and Z180 in thicknesses of 0,40 mm to 3 mm inclusive.

7.4 Surface treatments

- C: mill passivation
- P: mill phosphating
- O: oiling
- CO: mill passivation and oiling

ISO 3575:2005(E)

7.5 Base-metal designations

The base-metal quality designations are:

- 01: commercial quality
- 02: drawing quality
- 03: deep drawing quality
- 04: deep drawing special killed
- 05: extra deep drawing stabilized quality

7.6 Examples

7.6.1 An example of a complete designation is Z275NC02. This designation example includes the following components:

- Z: zinc coating
- 275: coating mass
- N: normal coating (as-produced)
- C: mill passivation
- 02: drawing quality

7.6.2 An example of a complete designation is ZF001SO04. This designation example includes the following components:

- ZF: zinc-iron alloy coating
- 001: coating mass
- S: normal coating (skin-passed)
- O: oiled
- 04: deep drawing special killed quality

8 Resubmission

8.1 The manufacturer may resubmit for acceptance the products that have been rejected during earlier inspection because of unsatisfactory properties after he has subjected them to a suitable treatment (selection, heat treatment) which, on request, will be indicated to the purchaser. In this case, the tests should be carried out as if they applied to a new lot.

8.2 The manufacturer has the right to present the rejected products to a new examination for compliance with the requirements for another quality or grade.

9 Workmanship

The zinc-coated steel sheet in cut lengths shall be free from amounts of laminations, surface flaws and other imperfections that are detrimental to subsequent appropriate processing. Processing for shipment in coils does not afford the manufacturer the opportunity to observe readily or to remove defective portions, as can be carried out for a cut-length product.

10 Inspection and acceptance

10.1 While not usually required for products covered by this International Standard, the purchaser may specify that inspection and tests for acceptance be observed prior to shipment from the manufacturer's works. In these cases, the manufacturer shall afford the purchaser's inspector all reasonable facilities to determine that the steel is being furnished in accordance with this International Standard.

10.2 Steel that is reported to be defective after arrival at the user's works shall be set aside, properly and correctly identified and adequately protected.

11 Marking

Unless otherwise stated, the following minimum requirements for identifying the steel shall be legibly stenciled on the top of each lift, or shown on a tag attached to each coil or shipping unit:

- a) the manufacturer's name or identifying brand;
- b) the number of this International Standard (ISO 3575:2005);
- c) the quality designation;
- d) the coating designation;
- e) the order number;
- f) the product dimensions;
- g) the lot number;
- h) the mass.

12 Information to be supplied by the purchaser

To specify requirements adequately according to this International Standard, enquiries and orders shall include the following information:

- a) the number of this International Standard (ISO 3575:2005);
- b) the name and designation of the material, for example, hot-dip zinc-coated steel sheet, Z275N02 (see Clause 7);
- c) dimensions: for cut lengths, thickness (combination of base metal and coating or base metal alone), width, length and bundle mass and the total quantity required; for coils, thickness (combination of base metal and coating or base metal alone), width, minimum or range of inside diameter, outside diameter, and the maximum acceptable coil mass, and the quantity required;

NOTE 1 When the base metal alone is specified, see Annex A for details.

NOTE 2 When the method of specifying thickness is not indicated, the combination of base metal and coating will be provided.

- d) the application (name of part) when available;

NOTE Identification of the application provides the opportunity to assess the compatibility of the end use with the ordered quality and coating designation. Proper identification of the part may include a description of the part, or a visual examination of a submitted part and/or prints, or any combination thereof.

ISO 3575:2005(E)

- e) ordering condition A or B (see 4.2);
- f) for drawing qualities 02, 03, 04 and 05, whether ordered to mechanical properties or to fabricate an identified part;
- g) whether oiled or not (see 4.6.3);
- h) whether mill passivated or not (see 4.6.1);
- i) whether mill phosphated or not (see 4.6.2);
- j) coating surface type (see 7.3);
- k) the report of the heat analysis (see 4.1), if required;
- l) inspection and tests for acceptance prior to shipment from the manufacturer's works, if required (see Clause 10).


EXAMPLE A typical ordering description is as follows:

International Standard ISO 3575, hot-dip zinc-coated steel sheet, Z275NCO02, 0,46 (base metal and coating) × 1 200 × 2 400 mm, 20 000 kg, to fabricate drawn shells, part 7201, ordering condition A, mill passivation and oiled, maximum lift 4 000 kg.

Annex A (normative)

Orders requiring base-metal thickness

A.1 When specified by the purchaser, the ordered thickness shall be the base-metal thickness. In these cases, the average coated-product thickness shall be calculated as the base-metal thickness + average thickness for each surface (see Table A.1) of the coating mass as indicated in Figure A.1. Thickness tolerance tables apply to the average coated-product thickness.

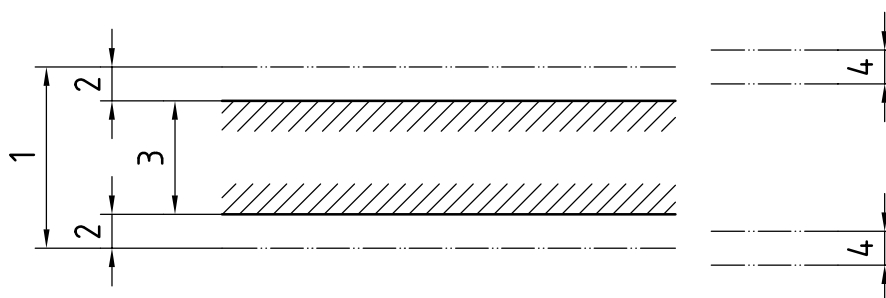

Key

- 1 average coated-product thickness
- 2 average coating thickness
- 3 base-metal thickness
- 4 thickness tolerance

Figure A.1 — Calculation of the average coated-product thickness

Table A.1 — Average thickness for coating mass — Total of both sides

Coating designation	Average coating thickness ^a for calculation mm
Z100	0,021
Z180	0,034
Z200	0,040
Z275	0,054
Z350	0,064
Z450	0,080
Z600	0,102
Z700	0,118
ZF100	0,021
ZF180	0,034
^a Coating mass data derived from actual production results.	

Bibliography

- [1] ISO 4998, *Continuous hot-dip zinc-coated carbon steel sheet of structural quality*
- [2] ASTM A653/A653M, *Steel Sheet, Zinc-Coated (Galvanized) or Zinc-Iron Alloy-Coated (Galvannealed) by the Hot-Dip Process*¹⁾
- [3] JIS G3302, *Hot-dip zinc-coated steel sheets and coils*¹⁾

© SABS

1) The relationship between national standards may only be approximate; therefore, the respective standards should be consulted for actual requirements. Those who use these documents should determine which specifications address their needs.